



Color for Life.

NATURAL
BLOOM





Contents

3 **Colorfully designed areas do not have to disappear from out of sight**

4 **Efflorescence is a natural phenomenon**

When white marks appear on the surface of colored paving blocks.

7 **Can efflorescence be rooted out?**

Maximum care in the production of the colored pavers is the best recipe.

Colorfully designed areas do not have to disappear from out of sight

Bayferrox® color pigments add life to pavers. They can be used to color any kind of stone; from earthy red, brown and black, all the way through to yellow.

The lightfastness and weather resistance of Bayferrox® pigments ensure that paving blocks keep their rich color over decades of intensive exposure to the elements. Even if a small chunk should break off, it goes unnoticed because of the integral coloring.

Occasionally we find areas with white patches on the surface, an effect known as 'efflorescence'. However, Bayferrox® cannot prevent efflorescence, nor can it cause it. Efflorescence must be seen for what it is: a sign of life from a product made of natural raw materials.



When white marks (efflorescence) appear on the surface of colored paving blocks – the dreaded phenomenon of efflorescence – the consumer’s initial happiness with his new pavers may well turn to annoyance. Some people may even suspect a production fault, but that is generally unfounded.

Efflorescence is a natural phenomenon


Colored paving blocks are made of concrete, a truly natural product. Concrete is made from sand, gravel, cement and water. It is also important to know that cement is made from a mixture of calcined limestone and clay.


As with all naturally-derived materials, there is variation in the

composition of these blocks. Water – in the form of rain, condensation or dew – penetrates through pores in the concrete of the finished blocks and partially dissolves the lime. The solution then migrates to the surface and the water evaporates, leaving a white lime haze which is not readily soluble.

Because the composition of the concrete – and thus also the lime content – is subject to certain fluctuations and because the influences of the weather also change (rain, snow, wind, cold, heat), the phenomenon of efflorescence appears with a markedly variable intensity.

The chemical process undergone by the lime when exposed to weathering is not quite

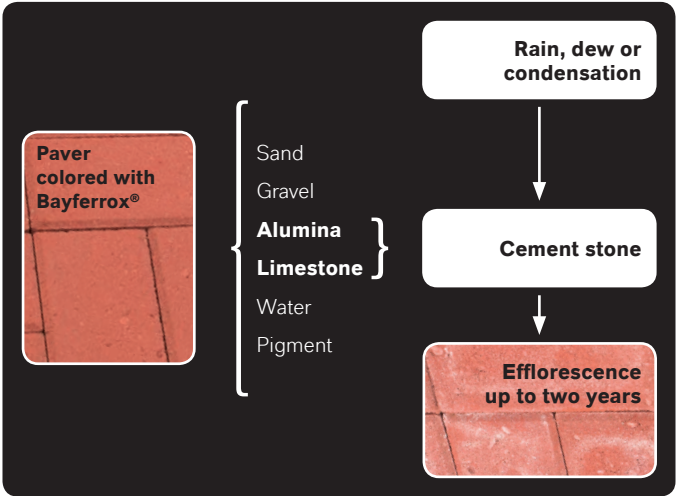


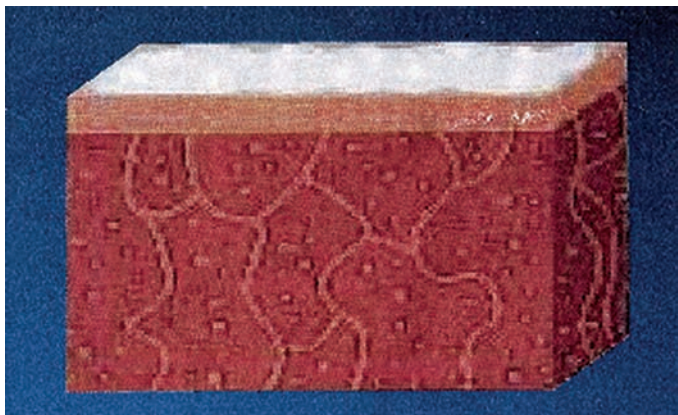

complete when it emerges on the surface of the stone. As a result of the rain and other elements, the lime is slowly

degraded and flushed away. In other words, efflorescence disappears on its own after a time.



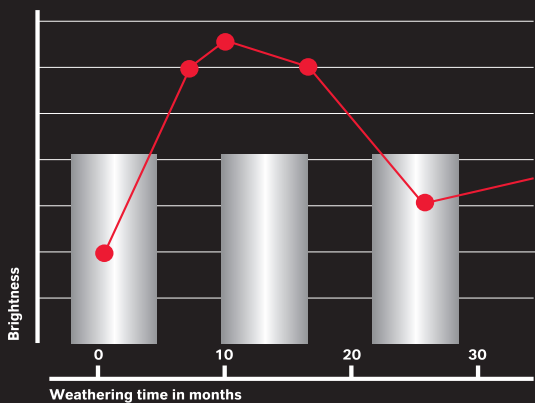

Because only the lime that has not been firmly bound by the other raw materials in the concrete can emerge on the surface, efflorescence generally

does not recur once it disappears. There is therefore little point in replacing the pavers or taking other measures to combat efflorescence.

Can efflorescence be rooted out?

Maximum care in the production of the colored pavers is the best recipe.

Modern production methods, intensive quality control and close cooperation between our technicians and manufacturers have proved extremely successful. Constant trials in weathering units, tests with various curing processes and other experiments have helped manufacturers to significantly improve the quality of

colored paving blocks in recent years. Whatever precautions are taken, it is important to accept that there is simply no economically viable process to reliably prevent efflorescence.

Since packaging film encourages the formation of condensation, the pavers should not be kept for long periods under plastic.



Efflorescence does not last forever

Efflorescence is generally washed off by the rain after about 1-2 years. Commercial products are available to anyone not wanting to wait that long. One advan-

tage here is that the lime in the upper layers of the concrete is also washed out. However, the surface of the stone may become rougher and the shade may change slightly.

X BAYFERROX® 
Color for Life.

Weathering of efflorescence



LANXESS Deutschland GmbH
Business Unit
Inorganic Pigments
47812 Krefeld
GERMANY
Tel.: +49 2151 88-7741
Fax: +49 2151 88-4133

www.lanxess.com
www.bayferrox.de

Health and Safety Information: Appropriate literature has been assembled which provides information concerning the health and safety precautions that must be observed when handling the LANXESS products mentioned in this publication. For materials mentioned which are not LANXESS products, appropriate industrial hygiene and other safety precautions recommended by their manufacturers should be followed. Before working with any of these products, you must read and become familiar with the available information on their hazards, proper use and handling. This cannot be overemphasized. Information is available in several forms, e.g., material safety data sheets, product information and product labels. Consult your LANXESS representative in Germany or contact the Regulatory Affairs and Product Safety Department of LANXESS Germany or – for business in the USA – the LANXESS Product Safety and Regulatory Affairs Department in Pittsburgh, Pennsylvania.

Regulatory Compliance Information: Some of the end uses of the products described in this publication must comply with applicable regulations, such as the FDA, BfR, NSF, USDA, and CPSC. If you have any questions on the regulatory status of these products, please consult your LANXESS representative in Germany or contact the Regulatory Affairs and Product Safety Department of LANXESS Germany or – for business in the USA – your LANXESS Corporation representative, the LANXESS Regulatory Affairs Manager in Pittsburgh, Pennsylvania.

The manner in which you use and the purpose to which you put and utilize our products, technical assistance and information (whether verbal, written or by way of production evaluations), including any suggested formulations and recommendations are beyond our control. Therefore, it is imperative that you test our products, technical assistance and information to determine to your own satisfaction whether they are suitable for your intended uses and applications. This application-specific analysis must at least include testing to determine suitability from a technical as well as health, safety, and environmental standpoint. Such testing has not necessarily been done by us. Unless we otherwise agree in writing, all products are sold strictly pursuant to the terms of our General Conditions of Sale and Delivery. All information and technical assistance is given without guarantee and is subject to change without notice. It is expressly understood and agreed that you assume and hereby expressly release us from all liability, in tort, contract or otherwise, incurred in connection with the use of our products, technical assistance, and information.

Any statement or recommendation not contained in this brochure is unauthorized and shall not bind us. Nothing herein shall be construed as a recommendation to use any product in conflict with industrial property rights such as patents covering any material or its use. No license is implied or in fact granted under the claims of industrial property rights such as patents. Edition 08/2011